


样品名称 4000#白刚玉	样品批号	统计方式 体积
测量日期 2025/8/7 14:36:25	小孔管孔径 50 μm	操作者
测试单位 东莞旭宝研磨材料有限公司	测量方式 定时间: 13 秒	

形状系数 6	样品密度(g/cm^3) 1.00	变异系数 21.73%
标准偏差(μm) 0.86	测量范围 0.4 ~ 256 μm	颗粒平均粒径(μm) 3.025
体积平均粒径(μm) 3.964	颗粒总数 26075	SSA($\text{sq.m}/\text{c.c.}$) 1.748
SSAW(m^2/g) 1.748		

Dx(3)(μm) 5.638	Dx(10)(μm) 5.043	Dx(50)(μm) 3.945
Dx(94)(μm) 2.690	Dx(0)(μm) 6.642	

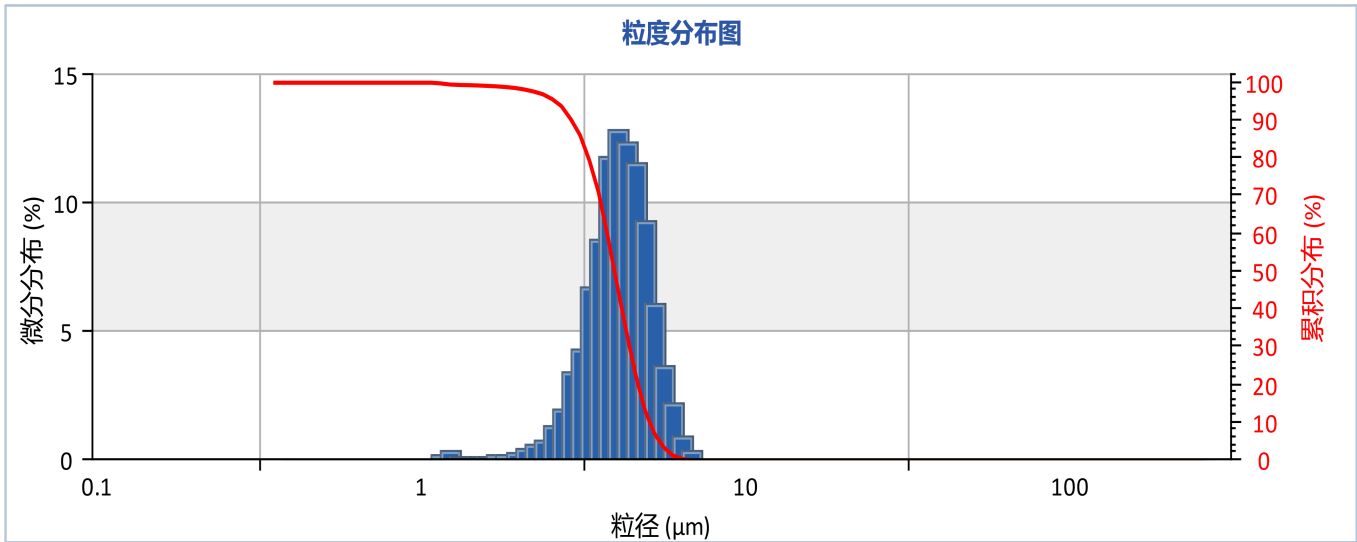

粒径(μm)	微分(%)	累积↓ (%)	粒径(μm)	微分(%)	累积↓ (%)	粒径(μm)	微分(%)	累积↓ (%)	粒径(μm)	微分(%)	累积↓ (%)
0.400	0.00	100.00	2.107	0.85	98.97	11.098	0.00	0.00	58.456	0.00	0.00
0.481	0.00	100.00	2.534	2.45	98.12	13.348	0.00	0.00	70.308	0.00	0.00
0.579	0.00	100.00	3.048	8.61	95.67	16.054	0.00	0.00	84.563	0.00	0.00
0.696	0.00	100.00	3.666	23.15	87.06	19.309	0.00	0.00	101.708	0.00	0.00
0.837	0.00	100.00	4.409	34.69	63.91	23.224	0.00	0.00	122.330	0.00	0.00
1.007	0.00	100.00	5.303	23.09	29.22	27.933	0.00	0.00	147.133	0.00	0.00
1.211	0.42	100.00	6.378	5.78	6.13	33.597	0.00	0.00	176.965	0.00	0.00
1.456	0.27	99.58	7.672	0.35	0.35	40.409	0.00	0.00	212.845	0.00	0.00
1.752	0.34	99.31	9.227	0.00	0.00	48.602	0.00	0.00	256.000	0.00	0.00